

Technical Note

High-temperature air channel testing of thermally bonded PVC geomembrane seams

T. D. Stark¹ and L. F. Pazmino²

¹Professor of Civil and Environmental Engineering, 2217 Newmark Civil Engineering Laboratory, University of Illinois, 205 N. Mathews Ave., Urbana, IL 61801, USA, Telephone: +1 217 333 7394, Telefax: +1 217 333 9464, E-mail: tstark@uiuc.edu

²Undergraduate Research Assistant, Department of Civil and Environmental Engineering, 2217 Newmark Civil Engineering Laboratory, University of Illinois, 205 N. Mathews Ave., Urbana, IL 61801, USA, Telephone: +1 217 333 7394, Telefax: +1 217 333 9464, E-mail: pazmino1@uiuc.edu

Received 10 July 2009, revised 19 December 2010, accepted 8 January 2011

ABSTRACT: The objective of this paper is to present a procedure for high sheet temperature air channel testing of dual-track thermal seams for 0.75 mm thick polyvinyl chloride (PVC) geomembranes. This objective is accomplished by developing relationships between seam peel strength and seam burst pressure for sheet temperatures ranging from 46.7°C to 62.8°C during field air channel testing. This paper extends the original relationships presented by Thomas *et al.* and Stark *et al.*, which extend only to 46.7°C, because a sheet temperature greater than 46.7°C is frequently encountered during hot summer months. The original relationship is extended to 62.8°C using the Arrhenius model, and a polynomial equation is presented that can be used to convert the sheet temperature during field air channel testing to the air channel pressure required to ensure that the specified seam peel strength of 2.6 N/mm is met or exceeded. Thus the proposed relationship and equation allow the seam peel strength to be verified by field air channel testing without conducting destructive tests.

KEYWORDS: Geosynthetics, PVC geomembrane, Air channel testing, Seams, Quality assurance, Quality control, Thermal welding, Peel strength, Burst pressure, High temperature

REFERENCE: Stark, T. D. & Pazmino, L. F. (2011). High-temperature air channel testing of thermally bonded PVC geomembrane seams. *Geosynthetics International*, 18, No. 2, 84–89. [doi: 10.1680/gein.2011.18.2.84]

1. INTRODUCTION

Thermal welding has proved to be a cost-effective method of field-seaming polyvinyl chloride (PVC) geomembranes, because PVC possesses excellent thermal welding characteristics, such as a wide thermal-seaming range, and surface preparation/grinding is not required. Thomas *et al.* (2003) show that fully automated thermal welding systems can allow the operator to adjust welder speed, nip-roller pressure and welding temperature to create high-quality seams for a range of geomembrane thicknesses. The welder should also be adjusted to account for variations in ambient temperature. Depending on the manufacturer of the welder, PVC welding temperatures vary from 315°C to 480°C. The use of thermal welding also allows common QA/QC techniques to be used for

PVC geomembranes, such as air channel testing, which is the focus of this paper.

Field-seaming is performed under a wide range of varying weather conditions, where sheet temperatures can easily reach high temperatures. Thus the prior relationship between sheet temperature and air channel pressure required to verify a seam peel strength of 2.6 N/mm for 0.75 mm thick PVC geomembranes presented by Stark *et al.* (2004) needed to be extended to sheet temperatures greater than 46.7°C. The main objective of this technical note is to present a relationship between seam peel strength and burst pressure at sheet temperatures greater than 46.7°C for 0.75 mm thick PVC geomembranes.

Stark *et al.* (2004) present relationships between seam peel strength and seam burst pressure at six different sheet temperatures, 5.3°C, 9.7°C, 14.8°C, 22.8°C, 35.0°C and

46.7°C, during field air channel testing. These relationships were used to construct a correlation between the field air channel pressure required to satisfy the required seam peel strength of 2.6 N/mm and a range of sheet temperatures during air channel testing. The correlation is extended herein to 62.8°C using an Arrhenius analysis of the test results. This correlation can be used to convert the sheet temperature during field air channel testing into the air channel pressure required to satisfy the specified seam peel strength of 2.6 N/mm without taking, or at least reducing the number of, destructive samples (Thomas and Stark 2003). The air channel test also challenges the peel strength along the entire length of the seam instead of the limited seam length that is used in conventional destructive tests. Most importantly, the air channel test inflates the flexible PVC geomembrane so the air channel is visible, and the integrity of the seam can be visually inspected along the entire seam length, as shown in Figure 1.

2. THERMAL SEAM EVALUATION

To make field thermal seams, it is necessary to melt the polymer at the sheet surface using a heat source. The heat can be transferred to the sheets to be welded from hot air and/or a hot-wedge welder. A hot-air welder uses an air blower that blows heated air from an electrical element between the two sheets to be bonded, and melts an interface strip. The use of hot air also helps to prepare or clean the seam area prior to seaming. A hot-wedge welder generates the heat necessary to melt the sheets at the



Figure 1. Air channel test performed in 0.75 mm PVC geomembrane seam

interface by electrical elements placed directly between two sheets. Nip rollers are used to drive the heating machine, and to apply pressure on the heated strip of the sheets (Mills and Stang 1997).

At present, two types of PVC thermal seam are used in practice: dual-track and single-track seams. Both types of seam can be created with a hot air or a hot wedge, and allow destructive and non-destructive testing to be performed as soon as the seam has cooled. This rapid assessment of quality allows immediate changes to be made in the seaming process to ensure optimal productivity. This paper focuses on non-destructive air channel testing of dual-track seams.

The thermally welded 0.75 mm thick PVC geomembrane seams presented by Stark *et al.* (2004) and used herein to extend the correlation were evaluated by the standard peel test at 50 mm/min at 22.8°C (ASTM D 6392) and by an air channel test developed by Thomas *et al.* (Thomas and Stark 2003; Thomas *et al.* 2003). The air channel test is performed by sealing off one end of a seam length and pressurising the other end with compressed air. The air channel test procedure used is different from the ASTM D 5820 procedure for pressurised air channel evaluation of dual-track seamed geomembranes. All of the equipment is the same as in ASTM D 5820, but the test procedure is different. In ASTM D 5820, the test procedure involves measuring a pressure drop in the air channel for a minimum of 2 min, and comparing this drop with the maximum allowable pressure drop to decide whether the seam is acceptable or not. In contrast, the air channel test used by Stark *et al.* (2004) to develop relationships between sheet temperature, burst pressure and seam peel strength involves selecting a starting air channel pressure and holding that air pressure constant for 30 s, then increasing the air pressure by 34.4 kPa, and holding the new air channel pressure constant for another 30 s. This multi-stage test procedure continues with air pressure increments of 34.4 kPa until the seam bursts. This allows a relationship between peel strength and burst pressure to be developed. The full procedure of the air channel test is described in Thomas *et al.* (2003). This procedure is the basis for the field air channel test procedure described in ASTM D 7177.

Thomas *et al.* (2003) show that the air channel test fails the seam from the inside towards the outside the seam, whereas the peel test fails the seam from the outside towards the inside of the seam. This difference is not deemed significant, because PVC seam requirements are specified in terms of peel strength, and the burst pressure during air channel testing is simply being correlated with this specified parameter. The specified value for the peel strength of both 0.75 and 1.00 mm thick PVC geomembrane seams according to the material specification available through ASTM D 7408 and the Fabricated Geomembrane Institute (FGI 2004) is 2.6 N/mm.

In the field, the relationships developed herein and a air channel test procedure slightly different from ASTM D 5820, described above, are used to determine whether the field seam is acceptable or not (see ASTM D 7177). The relationships between sheet temperature, burst pressure

and seam peel strength developed herein are used to determine the air pressure required to ensure that a field seam meets and/or exceeds a peel strength of 2.6 N/mm for sheet temperatures up to 62.8°C. The air channel is pressurised to the pressure required for a peel strength of 2.6 N/mm, which is obtained from the relationships presented herein, and this pressure is held for 30 s. If the seam maintains this pressure for 30 s, the peel strength is greater than 2.6 N/mm, as discussed in more detail below. The extended relationship for high sheet temperatures can be used with ASTM D 7177.

3. RELATIONSHIP BETWEEN SEAM PEEL STRENGTH AND BURST PRESSURE AT HIGH TEMPERATURES

New relationships between peel strength and burst pressure for air channel testing at sheet temperatures ranging from 46.7°C to 62.8°C are developed herein to extend the prior air channel testing relationship presented by Stark *et al.* (2004) and used in ASTM D 7177 for sheet temperatures ranging from 14.8°C to 46.7°C for 0.75 mm thick PVC geomembranes. The results of the Arrhenius analysis performed are plotted in Figure 2. The vertical axis is the natural logarithm (ln) of the slope of the relationships between peel strength and burst pressure for a given sheet temperature, as presented in Thomas *et al.* (2003) and Stark *et al.* (2004), which happens to be negative. Thus the vertical axis is labelled 'Rate', which means the rate of change in peel strength with burst pressure. The horizontal axis is the inverse of the sheet temperature. The data collected by Stark *et al.* (2004) are shown in solid circles, and fit a nearly linear trend line. This linear relationship supports validation of the use of the Arrhenius model for air channel testing. The extension to three new sheet temperatures, 54.4°C, 60.0°C and 62.8°C, is also shown (open circles) in Figure 2. The three points were selected to continue the linear relationship established by the prior data.

An important aspect of the linear relationship in Figure 2 is that it is used extend to sheet temperatures of 54.4°C, 60.0°C and 62.8°C. The extension maintains an R^2 value

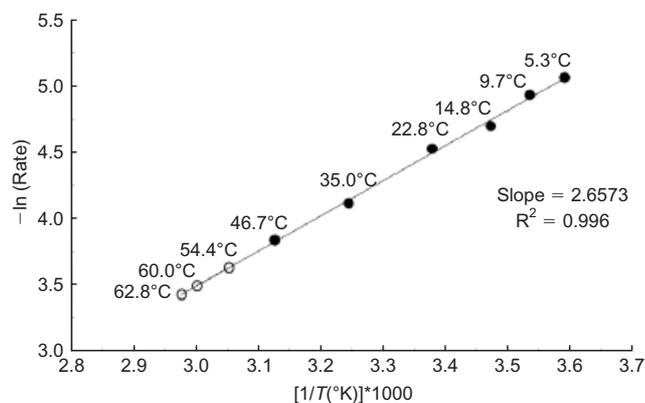


Figure 2. Arrhenius relationship between peel and burst pressure ratio to inverse sheet temperature

of 0.996. This R^2 value indicates a well-defined linear relationship, and it was deemed appropriate to extend the existing data from 46.7°C to 54.4°C. Based on this excellent agreement, and extending the relationship only from 46.7°C to 54.4°C, or 7.7°C, compared with the entire relationship, which extends from 5.3°C to 46.7°C, i.e. 41.4°C, additional testing to prove this small extension was deemed unnecessary.

The relationships between burst pressure and peel strength for the seams evaluated by Stark *et al.* (2004) are presented in Figure 3 as continuous lines, as well as the expected relationships from the Arrhenius analysis in Figure 2 as dashed lines. The slope of the trend lines for sheet temperatures of 54.4, 60.0 and 62.8 °C were obtained by extending the linear relationship in Figure 2. The trend lines in Figure 3 show that the ratio of peel strength to burst pressure decreases with decreasing sheet temperature during air channel testing. In other words, for a given peel strength, a greater burst pressure is expected as the sheet temperature decreases and the PVC geomembrane becomes stiffer. The ratios of peel strength to burst pressure for 0.75 mm thick PVC geomembranes from Stark *et al.* (2004) are summarised in Table 1, together with the ratios for sheet temperatures determined herein.

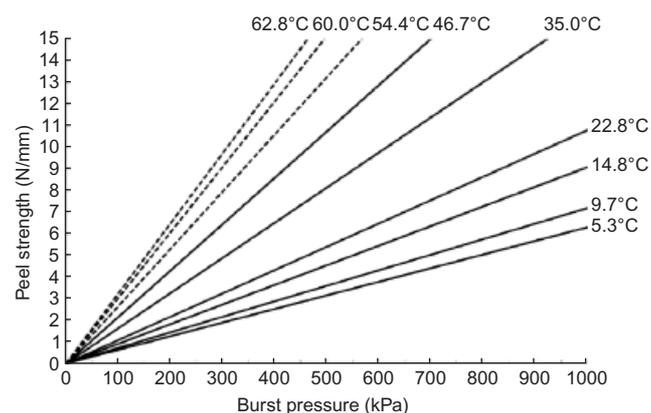


Figure 3. Relationships between burst pressure and peel strength for all non-film-tear bond (FTB) seams for various sheet temperatures

Table 1. Relationship between peel strength and burst pressure for various sheet temperatures

Sheet temperature during burst test (°C)	Measured slope from Stark <i>et al.</i> (2004)	Expected slope from Arrhenius analysis
5.3	0.0063	–
9.7	0.0072	–
14.8	0.0091	–
22.8	0.0108	–
35	0.0163	–
46.7	0.0215	–
54.4	–	0.0265
60	–	0.0304
62.8	–	0.0324

4. RELATIONSHIP BETWEEN SHEET TEMPERATURE AND REQUIRED AIR CHANNEL PRESSURE

It is proposed that the air channel test can be used as a non-destructive field quality assurance/quality control test instead of destructive sampling and testing of PVC geomembrane seams (Thomas and Stark 2003). Therefore it is necessary to develop a relationship between sheet temperature, burst pressure and peel strength. This relationship allows field personnel to determine the air channel pressure that is required for a particular sheet temperature to ensure that the measured seam peel strength exceeds 2.6 N/mm.

Table 1 shows that the ratio of peel strength to burst pressure is a function of sheet temperature during air channel testing. Thomas *et al.* (2003) and Stark *et al.* (2004) use the ratios for six sheet temperatures and the specified peel strength of 2.6 N/mm to calculate the minimum air channel pressure required to achieve the specified peel strength at sheet temperatures ranging from 5.3°C to 46.7°C for 0.75 mm thick PVC geomembranes. Six data points (solid circles) in Figure 4 denote these values, and were obtained by dividing the specified peel strength of 2.6 N/mm by the ratios of peel strength to burst pressure (shown in Table 1) at the six sheet temperatures. These six data points are from Stark *et al.* (2004).

To augment these data and extend the sheet temperature range beyond 46.7°C, the previously shown Arrhenius model (Koerner *et al.* 1992; Shelton and Bright 1993) was utilised to extend the non-linear relationship shown in Figure 4. Arrhenius modelling is typically used to determine the temperature dependence of chemical reactions, including deleterious reactions such as hydrolysis or oxidation, and has frequently been used to estimate the service lifetime of geosynthetics (Risseuw and Schmidt 1990; Koerner *et al.* 1992; Shelton and Bright 1993; Salman *et al.* 1998; Thomas 2002). The results of the

Arrhenius analysis were used to extend the relationship between sheet temperature, burst pressure and peel strength to sheet temperatures ranging from 46.7°C to 62.8°C. From Figure 4, the extension looks reasonable, based on the data for sheet temperatures below 46.7°C.

Considering the three new peel strength to burst pressure ratios for high sheet temperatures in Table 1, three data points (open circles) were added to Figure 4 that represent the air channel pressure required to satisfy the specified peel strength of 2.6 N/mm for sheet temperatures of 54.4°C, 60.0°C and 62.8°C for 0.75 mm thick PVC geomembranes. The result is the nine data points that correspond to the following polynomial equation for temperatures between 5.3°C and 62.8°C.

$$\begin{aligned} &\text{Required air channel pressure (kPa) to meet} \\ &\text{or exceed a peel strength of 2.6N/mm} \\ &= 0.0963 \times (\text{temp. in } ^\circ\text{C})^2 - 12.061 \\ &\quad \times (\text{temp. in } ^\circ\text{C}) + 464.39 \end{aligned} \quad (1)$$

This equation can be used to convert a sheet temperature to the air channel pressure required to satisfy the specified seam peel strength instead of graphically estimating the required air channel pressure or performing an Arrhenius analysis. Table 2 presents the nine data points in Figure 4 in tabular form, which may be easier to utilise in the field.

For comparison purposes, the relationship between sheet temperature and required air channel pressure required to meet or exceed a peel strength of 2.6 N/mm is compared with the values included in ASTM D 7177 in Figure 5. Figure 5 shows excellent agreement between the recommended relationship and ASTM D 7177 for sheet temperatures less than 46.7°C. Figure 5 also shows that the proposed extension is reasonable and fits the existing relationships (Stark *et al.* 2004; ASTM D 7177). It is also important to note that the six data points from Stark *et al.* (2004) were used to generate many intermediate points for

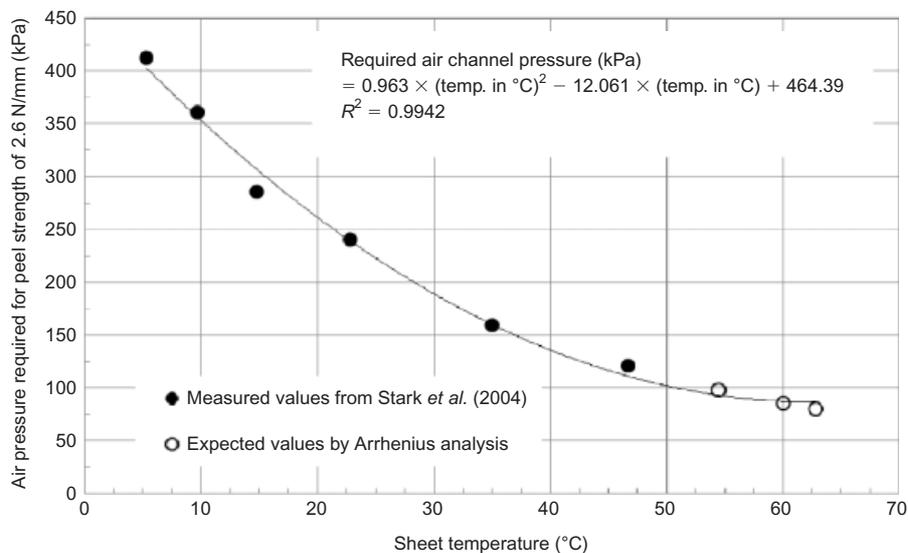


Figure 4. Recommend relationship between air channel pressure required to verify specified peel strength of 2.6 N/mm at various sheet temperatures

Table 2. Air channel pressure required to verify 2.6 N/mm seam peel strength for 0.75 mm and thicker PVC geomembranes

Sheet temperature (°C)	Air pressure (kPa)	Pressure hold time (s)
5.3	412.7	30
9.7	361.1	30
14.8	285.7	30
22.8	240.7	30
35	159.5	30
46.7	120.9	30
54.4	98	30
60	85.6	30
62.8	80.2	30

use in ASTM D 7177, because Figure 5 shows many more data points from ASTM D 7177 than Stark *et al.* (2004) report. This reinforces using the six data points from Stark *et al.* (2004) to extend the relationship to sheet temperatures greater than 46.7°C.

5. FIELD TEST PROCEDURE

To utilise the relationship proposed in Figure 4, field welding personnel can simply measure sheet temperature during air channel testing, and apply the required air channel pressure calculated from Equation 1 to the air channel or estimated from Figure 4; if the air channel maintains or holds the required air pressure for 30 s, the seam peel strength exceeds the specified peel strength of 2.6 N/mm for 0.75 mm thick PVC geomembranes. It is proposed that this procedure can be used instead of destructive seam testing, which has the disadvantage of cutting holes in the production geomembrane, patching the production geomembrane, and not testing 100% of the seam. The technique proposed herein evaluates 100% of the seam length, and the flexible nature of a PVC

geomembrane allows the inflated seam to be visually inspected over the entire length for defects (see Figure 1). The proposed air channel test can be performed on site at sheet temperatures ranging from 5.3°C to 62.8°C. Even though the data used herein were developed for 0.75 mm thick PVC geomembranes, it is anticipated that Equation 1 can be used for PVC geomembrane thicknesses of 0.75 mm or more.

While the air channel is inflated, the entire length of the seam should be inspected to ensure there is no blockage in the seam. If the seam inflates the entire length, there is no audible or visible evidence of air leakage, and the seam holds the pressure required in Figure 4 or Equation 1, then the peel strength of the seam exceeds 2.6 N/mm, and the seam passes the test. If the seam does not hold the required pressure, the seam fails, and the leak should be located by the sound of the leakage, or by isolating portions of the seam with another clamp. Portions of the failed seam can be isolated by folding the seam over itself and clamping the fold.

One other benefit of air channel testing of flexible PVC geomembranes is that the presence of aneurysms or slight seam defects can be detected (see Figure 6). An aneurysm is an area of the weld that did not seam completely because dirt, moisture, wrinkle or other deleterious material present in the weld area prevented the bonding of the geomembrane sheets in that area. It is recommended that a patch be placed over the aneurysm if greater than or equal to 50% of the seam width is unbonded. The percentage is calculated by dividing the length of the intrusion by the width of the uncompacted weld. The patch should extend 15 cm on all the sides of the aneurysm, parallel and perpendicular to the seam. If the seam has a flap – that is, the weld does not extend to the edge of the top geomembrane as shown in Figures 1 and 6 – the flap should be welded to the under geomembrane before patching. The flap can be welded easily and quickly in the field using a solvent or an adhesive. After welding the flap in the area of the patch, the patch can be applied

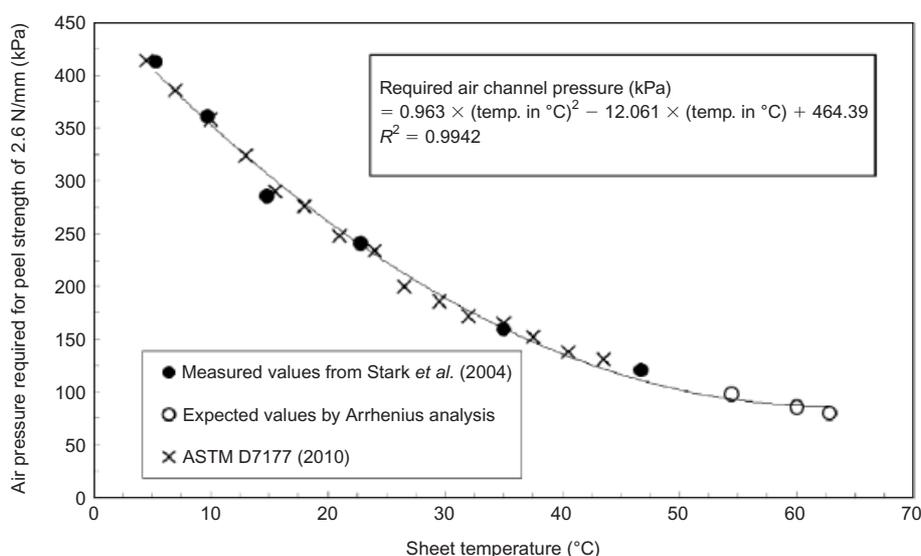


Figure 5. Comparison of recommend relationship between air channel pressure required to verify specified peel strength of 2.6 N/mm at various sheet temperatures with relationship included in ASTM D 7177



Figure 6. Aneurysm in 0.75 mm PVC geomembrane seam

using hot air, solvent or adhesive. If less than 50% of the seam is unbonded by the aneurysm, and the air channel maintains the required air pressure for a peel strength of 2.6 N/mm, then the seam is acceptable.

The air channel test presented herein is based on an air channel width of 15.9 ± 3.2 mm. For air channels greater or lesser in lay flat width, the hoop stress equation can be used to calculate the new air channel pressure to generate the same hoop stress (ASTM D 7177). The hoop stress equation is

$$S = \frac{PD}{2t} \quad (2)$$

where S is the hoop stress (kPa), P is the internal pressure (kPa), D is the outside diameter (mm), and t is the normal wall thickness (mm).

6. CONCLUSIONS

The purpose of this study is to extend the relationship between 0.75 mm thick PVC geomembrane sheet temperature and air channel pressure required to ensure that a seam peel strength of 2.6 N/mm is satisfied for sheet temperatures up to 62.8°C. The following conclusions are based on the data and interpretation presented in this paper.

1. The Arrhenius analysis performed shows an R^2 value of 0.996, which reinforces the use of this approach to develop a relationship between peel strength and burst pressure for the extended range of sheet temperatures.
2. The analysis presented herein is used to develop a polynomial equation to refine the relationship

presented by Stark *et al.* (2004) and extend the range of sheet temperature from 46.7°C to 62.8°C. The polynomial equation can be used to convert a sheet temperature during field air channel testing to the air channel pressure required to satisfy the specified seam peel strength of 2.6 N/mm instead of graphically finding the required air channel pressure or performing an Arrhenius analysis. Alternatively, the graph in Figure 4 or the tabulated values in Table 2 can be used in the field by welding personnel.

REFERENCES

- ASTM D 5820. *Standard Practice for Pressurized Air Channel Evaluation of Dual Seamed Geomembranes*, ASTM International, West Conshohocken, PA, USA.
- ASTM D 6392. *Standard Test Method for Determining the Geomembrane Seams Produced Using Thermo-Fusion Methods*, ASTM International, West Conshohocken, PA, USA.
- ASTM D 7177. *Standard Specification for Air Channel Evaluation of Polyvinyl Chloride (PVC) Dual Track Seamed Geomembranes*, ASTM International, West Conshohocken, PA, USA.
- ASTM D 7408. *Standard Specification for Non Reinforced PVC (Polyvinyl Chloride Air Channel Evaluation of Polyvinyl Chloride Geomembrane Seams*, ASTM International, West Conshohocken, PA, USA.
- FGI (Fabricated Geomembrane Institute) (2004). *PVC Geomembrane Material Specification 1104*, University of Illinois, Urbana, IL.
- Koerner, R. M., Lord, A. & Hsuan, Y. H. (1992). Arrhenius modeling to predict geosynthetic degradation. *Geotextiles and Geomembranes*, **11**, No. 2, 151–183.
- Mills, J. A. & Stang, J. R. (1997). Temperature corrected tensile strengths for geomembrane seams. *Proceedings of Geosynthetics '97 Conference*, Long Beach, CA, USA, pp. 439–451.
- Risseeuw, P. & Schmidt, H. M. (1990). Hydrolysis of HT polyester yarn in water at moderate temperatures. *Proceedings of the 4th International Conference on Geotextiles, Geomembranes, and Related Products*, The Hague, The Netherlands, pp. 691–696.
- Salman, A., Elias, V. & DiMillio, A. (1998). The effect of oxygen pressure, temperature and manufacturing processes on laboratory degradation of polypropylene geosynthetics. *Proceedings of the 6th International Conference on Geosynthetics*, Atlanta, GA, USA, pp. 683–690.
- Shelton, W. S. & Bright, D. G. (1993). Using the Arrhenius equation and rate expressions to predict the long-term behavior of geosynthetic polymers. *Proceedings of the Geosynthetics '93 Conference*, Vancouver, Canada, pp. 789–802.
- Stark, T. D., Choi, H. & Thomas, R. W. (2004). Low temperature air channel testing of thermally bonded PVC seams. *Geosynthetics International*, **11**, No. 6, 481–490.
- Thomas, R. W. (2002). Thermal oxidation of a polypropylene geotextile used in a geosynthetic clay liner. *Proceedings of the International Symposium IS Nuremberg 2002*, Nuremberg, Germany, pp. 87–96.
- Thomas, R. W. & Stark, T. D. (2003). Reduction of destructive tests for PVC seams. *Geotechnical Fabrics Report*, IFAI, pp. 26–29 March.
- Thomas, R. W., Stark, T. D. & Choi, H. (2003). Air channel testing of thermally bonded PVC geomembrane seams. *Geosynthetics International*, **10**, No. 2, 56–69.

The Editor welcomes discussion on all papers published in *Geosynthetics International*. Please email your contribution to discussion@geosynthetics-international.com by 15 October 2011.